

Zero Friction Cycling



***Detailed reviews are not really 70 pages long, there is a “Compendium of knowledge” at the bottom of each detail review. This is optional reading, the more you read, the more watts and \$ saving knowledge you will gain. Otherwise if just interested in detail review for lubricant – simply stop there.*

Lubricant On Test : Cyclestar Gold

Cost: \$70 Aud from Cyclestar (inc. Postage)

Size – 30ml



Photo :

Manufacturers Description on package;

Laser produced nano and carbon particle chain lubricant

Directions on package

- 1) Start with clean dry drivetrain
- 2) Shake for 5-10 seconds
- 3) Cycle Lube through pipette 2-3 times
- 4) Fill halfway
- 5) Rotate cranks
- 6) Hold applicator gently against chain, squeeze lightly to coat entire chain
- 7) Run through gears 2-3 times
- 8) Wipe off excess, enjoy ride

Extra information from Manufacturer website

Cycle Star was truly born out of love for cycling, and is the only commercialized product from Star Nanotech, LLC. Focused on research, and primarily government contracted, we are a company founded on discoveries in the unique properties of nano materials, specifically when used in the design of lubricants. Our main laboratory is located on the Centennial Campus, an R&D park at NC State University, with the Cycle Star offices and an additional manufacturing facility currently under construction in Mebane, NC.

Our globally patented method of producing nanoparticles by laser synthesis delivers structures much more precisely, and with greater specificity than current production standards that rely on magnets or chemical processes. Without the use of chemicals, Teflon or wax, our material additives employ a unique combination of super hard nano and softer microparticles to reduce friction and wear on multiple fronts by :

- Polishing and permanently filling microscopic peaks and gaps on a molecular level, a hypersmooth surface is created that requires less lubricant and stays clean by not allowing dirt to cling in the first place.
- Mixing in particles designed to act as ball bearings, friction is further reduced.
- All of the structures working together to produce enough of a charge to repel dirt before surface contact, preventing buildup and wear from foreign contaminants.

The first bicycle-specific mixture was formulated over the summer of 2016, with early tests proving promising enough for the Holowesko | Citadel pb Hincapie Race Team to choose Cycle Star as a technical supplier before it even had a name.

"If a little is good more must be better". Although that may not always be true, the concentration of the specially formulated nano-particles do make a difference in friction and dirt repelling properties. Thus, we have doubled the concentration of the nano-particles over the standard (Red Label) Cycle Star Lube to produce our Black Label version and we have doubled it yet again for our top of the line Gold Label.

Although just a "dab will do you", well actually 1/2 a dropper full of Cycle Star Lube, check out what a difference the higher concentration Black and Gold Label versions of the lube that the pro Holowesko-Citadel racing team is using in their stellar 2017 campaign. You will be amazed by the silence and the smoothness of your drive train.

Extra information included in a letter that came with the delivery of Cycle Star Gold.

Your shop is one of 116 prestigious, hand picked US dealers chosen to introduce Cycle Star Nanotech. Within this package we've included our first product; a chain and drivetrain lubricant. Head mechanics shall reserve first usage rights, as is law, but we highly encourage sharing this with customers and staff... especially anyone that is a known skeptic of anything new. On the reverse side you will find expanded application instructions, follow them to ensure you are getting the most out of Cycle Star application, which has been proven to last over 1000k miles in good conditions when applied to a clean chain. That might be a pretty tall claim, so we recommend you experience it for yourself.

*****Note I am hardly a prestigious hand picked US dealer – this is the letter that came with the bottle I purchased from their webstore, shipped to little ZFC is Australia.... Hmmm.....***

The letter continues.....

Who we are can easily be summed up by who we ain't.

Cycle Star does not exist to simply sell a product, and is by no means a marketing machine. We are the bicycle products spur of Star Nanotech, a North Carolina State University partner and DOD / DARPA contractor founded on the unique properties of nanotechnology, specifically when used in lubricants. We are currently the only manufacturer utilising lasers to hone carbon nanoparticles, creating structures much more specific and effective than current standards that rely on chemical vapors or magnets for production.

This is a materially enhanced lubricant that will make any drivetrain noticeably smoother, quieting things down immediately, then continues to stay much cleaner much longer than expected. Carried in a lightweight synthetic oil, it does not require ultrasonic application to be completely effective, and achieves everything mentioned without the use of chemical additives, waxes or PTFE. It has been subjected to aerospace grade tribology tests, and is shown to reduce friction well beyond the other nano enhanced lubes being produced. We are still awaiting independent bicycle specific dyno testing, but found that the difference is perceptible enough that it might surprise a few people when such data comes out.

Any extra detailed information re application and usage from website;

Same as on bottle just more wordy.

Clean Chain Efficiency rating: **Poor – 6.76w as per Friction Facts testing (45th of 54 lubes tested)**

Viscosity: Thick – 1ml moved 5.5cm in 10 seconds on 30dg angle.

Test stops when net chain wear reaches 0.5mm+

Cycle Star Gold Main Test Results

Block (each 1000km)	Wear measure (mm)	Inc. On previous measure	% Wear for block (0.5mm=100%)	% Wear rate per 100km	Comments / Observations
0 – Initial check measure	0.113	n/a	n/a	n/a	Shimano chains usually measure 0.1 to 0.15mm from new.
1 – No contamination	0.224	0.111	22.3%	2.23%	That is a high wear rate indeed. Not as hoped from marketing re amazing tech and the price.
2 – Dry contamination	0.379	0.154	30.9%	3.1%	A fairly notable jump in wear from contamination – the gritty running was very audible and easily felt, chain became very dirty.
3 – No added contamination	0.604	0.226	45.1%	4.51%	What we look for here is a lubricants ability to clear some of the contamination from block 2. A decrease in wear rate from block 2 is expected, even if it is not able to return to block 1 wear rate. The fact the wear rate continued to degrade despite no further added contamination shows CS Gold has no ability to clear contamination. The increase in wear despite being a no added contamination block is very high.
4 – Wet contamination	n/a	n/a	n/a	n/a	Not tested as past wear allowance.
5 – No added contamination	n/a	n/a	n/a	n/a	Not tested as past wear allowance.

Extrapolated wear based on blocks 1-5 = 3052km

Extreme Contamination Block (chain cleaned again prior to test)

Start wear measure	500km measure	1000km or end of test measure & km	% Wear for block (0.5mm=100%)	% wear rate per 100km	Comments / Observations
n/a	n/a	n/a	n/a	n/a	Not tested due to previous wear rates.

Single Application Longevity test (Chain Cleaned Prior to test – no added contamination – Cumulative wear checked every 250km) – allowed extra 0.25mm on top of end of block 1-6 wear measure

Start wear measure	% wear 250km	% wear 500km	% wear 750km	% wear 1000km	% Wear 1250km	% wear 1500km	
n/a	n/a	n/a	N/a	N/a	N/a	N/a	Based on block 1 -3 results a single application longevity test was not worth the resources. It appears as though a single application would be long lasting, however the wear rate and friction would be poor. Having a long lasting application of high friction and wear is not what ZFC is on the hunt to find.

Test observations and review

Cycle Star Gold is another company that talks up a lot of technology and makes some very big claims around performance, however provides no actual data to back it up.

I wrote to them re their performance testing data, advising if they can supply some information to back the performance of the lubricant I would definitely be keen to be a retailer. If this product performs as per claims, I most certainly would love to stock. I heard nothing back.

Road.cc did a better than average online lube review and wrote to them for some data, and heard nothing back. So they had Jason Smith of Friction Facts test, and the results were not impressive.

When I last spoke with Jason Smith he advised they use a high grade mineral oil to calibrate the test machine which comes out at 6w. Cycle Star Gold claim their laser crafted nano tech is put into a light synthetic oil. Attaining a 6.76w efficiency result – something is wrong. A light synthetic oil should not be slower than 6w, so either something is up with this oil, or their amazing laser nano tech is the most expensive way devised thus far to make light synthetic oil slower.

It has a fairly heavy viscosity – certainly not what I would describe as a light oil, but I guess this depends on each persons definition of light. Compared to the oil you put in your car engine, sure – it is light. Compared to a lot of other bicycle lubricants – it is quite heavy. As per Friction Facts testing - better results were attained when applying more than recommended. Cycle Star have fallen into a trap that has caught a few manufacturers out – in a bid to impress potential buyers re the amazingly small amount of their product one needs to use – the initial application instructions can fall well short of what is required to ensure a properly cleaned chain is subsequently properly lubricated. It is costing customers friction and parts wear in a bid to impress with apparently only needing to use a tiny amount. (**Silca fell into this trap with its NFS lube which has frankly ridiculous initial application instruction on bottle – thankfully they have amended on their website since FF testing, but many consumers will still be caught out*).

So for initial application I added a drop per link and worked it in with 50 crank revolutions in small chain ring and 11t cog. I re applied with a drop per link and continued same for re lubes.

Nevertheless – block one wear rate came in at a very disappointing at 22.3%. And using a drop per link, even when wiping excess, things were getting messy.

Block 2 – Similar to Muc-Off hydrodynamic and Nano lubes – Cycle Star Gold really soaks up the contamination. I may refer back to a particular marketing claim here;

- Polishing and permanently filling microscopic peaks and gaps on a molecular level, a hypersmooth surface is created that requires less lubricant and stays clean by not allowing dirt to cling in the first place.
- All of the structures working together to produce enough of a charge to repel dirt before surface contact, preventing buildup and wear from foreign contaminants.

Well, I hate to ruin the party here but the above was simply not demonstrated. At all. Cycle Star Gold readily soaked up all contamination. It sounded, felt and looked pretty bad. I would not take this product off road.

Note also re above claims – filling microscopic peaks to make a smooth surface makes sense. This is what MSW / UFO / Paraffin does extremely well. Other lubes claim to do it, and may well do it – the challenge liquid lubricants have is they gather airborne dust and other abrasive contamination at a fast rate. This contamination is merrily abrading new furrows, so it is quite a tussle for liquid lubes to achieve this nice smooth surface. It is also trying to achieve it on metal. With immersive waxing, there are two solid wax surfaces sliding against each other, and the wax surfaces polish each other up very quickly and effectively. And the key of course is that being solid and therefore with extremely low amount of contamination getting in to mess things up. Wax coating all surfaces of chain metal also neatly takes care of peaks and fissures – especially after initial chain break in.

Regarding claim of polishing metal surface – Pro link gold also claims this, as part of its “metal conditioning”, and it also Friction tested poorly. Apparently it gets better over time, but this has yet to be proven. What I do know is that if you are attempting to polish hardened steel – it simply has to take some friction to do so. Set to polishing something with a frictionless cloth, nothing would happen. This approach to achieving a low friction lubricant (excuse pun) doesn’t make intuitive sense, and so far in the lubricants claiming this – they are not exactly slamming it in the lab (Pro Link Gold was 50th place). And so thus far efficiency testing is backing intuitive thoughts that polishing metal will take some level of friction to achieve.

Now another of their claims;

- **Mixing in particles designed to act as ball bearings, friction is further reduced.**

Again – this just does not make intuitive sense. So they are polishing metal and filling in fissures to create a “hypersmooth” surface (I didn’t know that was a word either), and instead of having two hypersmooth surfaces sliding on each other (one of the reasons MSW / UFO etc are so fast so quickly) they are sticking in billions of the worlds tiniest ball bearings for them to articulate on. Jason Smith calculated that the surface pressure on the internal chain parts under articulation can approach around 4000psi. It is hard to imagine that billions of ball bearings would be the way to go vs two hypersmooth surfaces sliding across each other. Again the performance results – Both Friction Facts and ZFC, are demonstrating that claims are not translating to real world performance. The claims do not make sense logically, and the intuitive logic was not challenged at all by the results.

And unfortunately – all of these wonderful claims are let down by the fact that this bit - **“All of the structures working together to produce enough of a charge to repel dirt before surface contact, preventing buildup and wear from foreign contaminants”** simply didn’t happen. Unfortunately if anything there was an attractive charge, contamination was readily absorbed indeed.

No matter how amazing a liquid lubricant is in the lab – once one starts using outside the lab and riding in the real world with airborne dust and abrasive contamination that is readily absorbed by liquid lubes, things often go downhill quickly. Most manufacturers focus on this aspect heavily in

their marketing, with claims of “cleaning as it lubricates”, and “forms protective film or membrane to prevent contamination wearing against metal” abound, but in reality the level any lubricants achieve these claims tends to be poor at best. Some lubricants have shown an ability to do some level of cleaning, however a lot of contamination is still left behind. Some lubricants show a much greater resistance to absorbing dry contamination, but typically have no ability to clear what does get in. However – since manufacturers can typically claim whatever they like and provide nothing to back claims – it is fairly open slather to write whatever they like on the bottle / website. (and unfortunately we have seen some pretty blatant use of incorrect testing and data for products that do back marketing claims with performance testing).

Anyway back to the test - So dry contamination block 2, things went downhill a fair bit – but not the worst we have seen. Block 3 where no further contamination is added is a lubricants chance to prove it has some ability to clean as is lube / clear some contamination. What is a fairly text book example of this happening is what was observed for Rock n Roll Gold – which recorded 8.9% wear in clean block 1, increased to 28.9% in dry contamination block 2, and decreased back to 20% in clean block 3. So it could not return to same as its first 1000km block where it starts with a perfectly clean chain, but it was able to measurably improve on Block 2 wear rate by clearing some contamination out.

Cycle Star Gold recorded a whopping 45.1% for block 3, over double block 2 wear rate. So it simply does not clear anything. No doubt if I had wear check measured every 100km during block 2, I would have seen the wear rate simply continue to build and build as the level of abrasive contamination in the chain / lubricant continued to build up. By the end of the last addition of contaminant in block 2 – it is as much grinding paste as it is lubricant, and so even with no further contamination added in block 3, what was gathered went nowhere and continued to eat through chain metal.

Just like Muc Off Hydrodynamic and Nano – this was easily felt as well. Turning the cranks by hand on re lube and to wind up neo before starting motor for next interval, you could just feel all the grit crunching away in the chain, and if you grabbed a section of chain and moved laterally you just felt all the grit crunching in your fingers. It does not feel pleasant that this is what is lubricating your hardest working mechanical part.

A good test for what you think is happening with your chain is to ask yourself – would take what you can wipe off your chain and add that to your bearings? If you think it would probably add gritty abrasive stuff to your bearings and cause them to run poorly and wear out quickly – why

would you be happy for that to be the lubricant for the part working so much harder than your bearings? It is why people are often surprised that one can easily save so many watts simply by ensuring their hardest working part is lubricated by a clean, fast lubricant that truly stays clean, vs running an abrasive paste through 20,000 articulations a minute under thousands of PSI load.

It is why ZFC focusses so much on real world performance of chains & lubricants. Chains and lubes are where the easy low hanging fruit of friction savings are found, or lots of easily avoidable friction added.

Another interesting fact for CycleStar Nano – if you are prone to getting chain ring tattoo's, well this will really be fun for you. Things were getting quite messy and sometimes I have to do some maintenance on the coupling joining gearbox to chainset etc, and a couple of times reaching around my arm would touch chain on big chain ring. I thought for a while I might have an actual permanent tattoo. A few days and good showers later and its fading, a week or so for the stain to completely go. It is something else.

One will have noted from the marketing that a US pro team is using the product – Cycle Star still tout this quite highly on their facebook page and website. I will wait until that partnership ends, and then email team and see if I can get some info from mechanics re how they found it. (I can't ask them whilst still being sponsored as they have to say it is amazing of course ☺).

If it was a cheap lube, I would have lesser expectations. But it is a really expensive lubricant – at \$70aud delivered for 30ml. Even with a low usage amount, that is darn expensive.

However mostly it is the marketing claims that and lack of evidence or performance vs the claims that really let this product down. And in view the manufacturer along with it. In their letter they state they are not a marketing machine, but my oh my they make some pretty huge claims about their product and tech, none of which are backed by data, they don't answer you if you request some data – which frankly I always find is plain suspect – the Friction Facts testing result was poor however it matched the intuitive flaws in their claims, and my ZFC testing showed a very high wear rate, a high rate of gathering contamination, no ability to clear contamination – and thus performance outside the lab is even worse than performance inside the lab.

Cycle Star claim they have had their product “Tribology” tested (at aerospace grade levels no less) – I had to Wikipedia that, and at the moment I must say I don’t have a full grasp on this testing and how it would translate to performance as a bicycle chain lubricant. I gather Cycle Star don’t either – because if there was a nice clear correlation from the Tribology testing to show how awesome its performance is as a chain lubricant, this would accompany all the marketing would it not?! One could not wait to show the world the proof that their product is the one you should buy above your competitors?

Again this stuff just doesn’t pass muster / logic with me.

Let us bring this back to the basics. Not to go over old ground too much but;

They make some very big claims such as

- Polishing and permanently filling microscopic peaks and gaps on a molecular level, a hypersmooth surface is created that requires less lubricant and stays clean by not allowing dirt to cling in the first place.
- All of the structures working together to produce enough of a charge to repel dirt before surface contact, preventing buildup and wear from foreign contaminants.

Let us assume that they would not make these claims unless they had the above tested and proven. Surely a manufacturer is not going to release a product with such performance claims and at that price, without having thoroughly tested and proven that these claims are true. In my opinion no company of any integrity would do such a thing as claim some amazing performance, charge a huge price, but have not in fact determined that it does do what they claim.

So I am assuming Cycle Star did in fact test and prove their lube does the above – so where is it? Why isn’t it on the website? Why do they not answer when you ask for testing / data? Where is their long coming bicycle dyno testing and why wasn’t this done – both lab and after extreme conditions riding – before making the above claims?

If I, or a company I owned – invented a drip lubricant that achieved the above claims and I had the test data to prove it – you couldn't shut me up about it if you tried. I would be shoving the proof at you from every angle I could think of.

I'm not going to type anything overt – but I just don't like the feel of what is going on here – it doesn't make sense to me on any level. And the testing we do have now for this product from FF and myself at ZFC – it is not promising.

ZFC Overall Performance Ratings

Race Day Lubricant Road – 3/10

It starts slow, and gets slower as it gathers contamination.

Race Day Lubricant - MTB / CX – 1/10

I would not take this lubricant near dust or dirt.

Everyday Lubricant – 1/10

Very expensive and poor wear rates. Messy. Stains skin / clothing badly on slight contact.

Harsh Conditions Lubricant – 3/10

CS Gold did not make it to the wet contamination block, however it appears as though it would not wash away easily. However all contamination will stick to it, and it is slow and high wearing to begin with – so whilst I'm giving it a couple of points re it will likely stay put and perform some level of lubrication during harsh wet rides – there are simply a lot of much better options to choose from, most of which are a lot cheaper.

Single Application for Long event – ?/10

I did not bother with the resources and equipment wear to test based on the performance of blocks 1-3. It does appear to be a long lasting lubricant, however a single application that lasts a long time is still not a lot of use if it is delivering high friction and wear.

Cost to lubricate (based on blocks 1-5)

The small 50ml bottles do go a long way, however at \$106.50 per 50ml bottle, the cost of this lube is way above anything else. It needed to be offset by delivering amazingly low friction and parts wear rates, however the exact opposite was seen with parts wear rates well above any other lubricant tested to date. Added together, running Muc-Off Nano as your daily lube is for millionaires only.

Extrapolated drive train running costs table per 10,000km based on blocks 1-5.

(Cost per km of lubricant & assume 2 x chains @0.5mm wear per cassette & 6 x chains per set of chain rings. Australian online + Lbs store RRP prices of ultegra cassettes and chain rings) .

Lubricant cost per 10,00km	Chains per 10,000km (\$40 per chain)	Number of cassettes worn per 10,000km & cost (\$90 per cassette)	Chain rings cost per 10,000km (\$195 set).	Total Drive train running cost per 10,000km
\$154.00	3.3 = \$132.00	1.6 = \$144.00	0.55 = \$107.25	\$537.25

(0.6bottles used for 3000km, 3.3 chains, 1.6 cassettes, 0.55 chain rings.

Pictures from test



Post first 400km interval chain wipe. First 400km not bad at all re cleanliness. It didn't stay that way as test went on, however I tend to err on the side of safety re amount of lubricant.



End of main test – 3000km. Not the best.



End of main test – 3000km. Cassette and chain don't look as bad as some, however the amount of lubricant that was flung off to coat everything in the vicinity was pretty bad. I may have slightly over lubricated vs instructions to ensure best chance of good performance during contamination block, but still I only used 20ml across 3000km – so not exactly throwing lube on either.







End of test – 3000km mark. It was a fair bit of work to clean cassette, chain rings and jockey wheels, and all the test equipment. It would have taken a lot of product and time to properly clean chain for single application longevity test had I bothered to test it. It wasn't worth it.

Best internet reviews for Cycle Star Gold here;

<http://road.cc/content/review/222828-cycle-star-nanotech-lube-15ml>

<https://www.bikerumor.com/2016/12/01/cycle-star-rolls-your-chain-on-laser-crafted-nanotech-lube/>

I do like in the bikerumor review where it is talking of CS gold claims to be faster than wax and doesn't need to..... *"use some complicated heated or ultrasonic application"***.

For the record – turning a slow cooker switch from "off" position to "Low" to melt wax, I personally do not find to be a ***complicated heating application***. It is just as complicated as turning kettle on to boil water. If you can boil a kettle, you can melt wax in slow cooker. It is amazing how often drip lube manufacturers try to paint immersive waxing as some onerous complicated process. Turn slow cooker on – wax melts – swish chain in wax. Complicated?

Lube Logic – Little Compendium of knowledge to save you \$ and lost watts.

In the information below I go through a number of the main claims made by manufacturers, run through a bit of a reality check, and help provide a base understanding re how things may or may not work. Some lubes are getting pretty fancy – and some are VERY expensive.

Does your lube clean as it lubes? Does it form a protective membrane? Does it “condition” the metal? Is it PTFE based, or wax, or mineral oil, synthetic oil, or ceramic tech, or nano tech, or contain laser crafted micro balls? Is it a dry lube? wet lube? What is most important to you – outright efficiency? Longevity? Cleanliness? Cost to run? Do you have different needs for your TT bike vs your road bike vs your cx or mountain bike?

The below should help you make an informed decision on what is the right lube/s for you, and this information will continue to update as our testing reveals actual performance vs claims.

Lube testing – what are we looking for and why should you care?

Your chain is your hardest working part by miles, and it is working completely exposed to dust, grit, water, mud. Friction Facts testing was ground breaking and they really shone a light into the dark art of drive train friction. However, outright efficiency on a clean chain in clean lab environment tells only one part of the story.

Data on lubricant performance once contaminated is extremely scarce - and yet most performance claims centre around how the lubricant deals with contamination – cleans as lubes, forms protective films / membranes etc. They boast about many awesome things the lubricant apparently does whilst you are out riding around in the real world – but where is the testing and data for this?!

Considering that the biggest impact to a lubricant and therefore a chains performance is contamination, and that all chains are subject to dealing with this from km zero in the real world – there is a big gap of actual performance testing and data here.

Friction Facts did do a simulated longevity test across 8 lubricants representing main lubricant types (PFPE, wax, wax based, ceramic etc..). Lubricants were tested at the start, run for an hour dripping on water and sand, and tested again at the end. Some lubricants had very little shift in friction, some increased notably, and one which tested well when clean increased by 3.8w. That's in one hour.

So how a lubricant performs on a clean chain in a lab is no indication as to how the lubricant will perform once you start riding it.

How well a lubricant does or does not handle contamination depends on many, many factors. What is the actual lubrication type? What is the carrier fluid? What is the ratio of lubricant to carrier fluid? Is your lubricant actually capable of achieving the big claims it is making regarding forming protective membranes, preventing metal to metal contact or contamination to metal contact from wearing your chain metal? Does it really clean as it lubes?

Testing lubricants in a controlled longevity test is the key piece of the picture. It is all well and good to have a lube that tests very low friction on a clean chain, but if it has doubled that friction performance in few hundred km of riding then this is rather important to know. If a lubricant is fine for a 90 minute or 4 hour test but becomes very poor over thousands of km's without frequent full solvent cleaning intervention to reset contamination – that is important to know – a large percentage of cyclists just keep dripping more lube on with little to no proper chain cleaning maintenance.

The main state of play at the moment is there is either no known or accessible testing data provided by a manufacturer, or if there is data there is no detail available on the testing protocol. We also have a rather fun situation at the moment where two major players in the industry – Ceramic Speed and Muc Off – both with a lot of very fancy testing equipment – are providing test results completely at odds with each other. One of them is incorrect. Both claim to have developed the fastest lubes and chains. Any reader who has gone through the pages and pages of info from both sites would be left quite confused and with no way of determining who is right and who is wrong (at the time of writing I am trying to clarify the testing and results from both parties).

There are also times when a lubricant may perform well if a different lubrication protocol is followed vs manufacturer instructions. Sometimes the lubricant itself may be quite good, and would perform well if the amount / re lube frequency was adjusted – however it is let down by overstated marketing claims of extreme longevity performance, or the very low amount that should be added so the purchaser can expect a vast amount of km from a single small bottle etc. There are times when sales and marketing undermine what would have been an overall fine performing lubricant if a more logical approach for that type of lube was followed.

Very little proper longevity testing has been done. Simulated lab tests have typically been between 1 hour and 4 hours long, and other longevity testing has typically been done via real world riding as who is going to run equipment for thousands upon thousands of km's per test. However real world riding is unfortunately a very inaccurate way to conduct longevity testing as there are just too many variables in the key aspects that affect chain wear. Just going out riding and training subjects chains to different loads for different times, and contamination levels that are at both varying rates and introduced at varying times in the chains lifespan.

If in my testing I subjected the lubricants on test to different loads for different times and introduced different levels of contamination at different times in the chains lifespan – I don't expect anyone would place much stock in the testing results. No proper testing process I can think of would accept such variability in the key aspects of the testing and expect anyone to accept the results. Yet that is what we have with longevity testing completed via real world riding.

Also, as the testing relies on the correlation between chain wear rates from abrasive friction, very accurate measuring of net chain wear is a mission critical component. However any other longevity tests I have seen using this correlation have simply used an analogue checker unable to deliver precise wear measures. And dismayingly chain preparation can also be off the mark – with chains prepped simply by wiping the outside – leaving factory lube inside to which the lube on test is added. Not good. Added on top of the variables in load / time and contamination – you can get an idea as to how accurate some testing results may be.

At ZFC we want to ensure we stock the genuine best in class products & chain lubes to cover your type of riding and racing – be it the best for a prologue TT, a 24hr enduro, a full mudder cx, your daily commute, and every range in between. We want to have a selection of the best products depending on your level of maintenance comfort. We want to be able to demonstrate accurately the total running costs of one lubricant vs another taking into account the cost of the lubricant, usage rate and parts wear rate. We want customers to understand more about why their chains typically contribute more friction to their drivetrain than all of their bearings combined, and just how many watts (and \$\$) can be easily saved with the right lubricant. We want to know what a lubricants limitations are – what performs great when dry but atrocious when wet etc. And lastly we want to help consumers understand what is happening inside their chain and just how difficult some of the manufacturers claims are to actually execute in real life.

So for the worlds first proper longevity testing – ZFC have kept things simple equipment wise but extremely robust in process. We do not have microprocessor controlled instruments accurate to 0.02w worth tens of thousands of \$, what we do have is equipment that can be afforded to be run for thousands of km's and up to around 200 hours per test. Due to the correlation between friction and chain wear, ascertaining a lubricants performance via running chain through an actual bicycle drivetrain whilst alternating through specific clean and contamination blocks delivers a lubricant performance breakdown to a level that has not remotely been provided previously. With all the fancy equipment of

the big manufacturers you get a start friction figure and an end of test friction figure after usually somewhere between 90 minutes and 4hrs of testing. Whereas ZFC testing can assess the strengths and limitations of a lubricant through each specific clean or contamination run block and provide a full breakdown of a lubricants performance across each, as well as assessing claims vs reality – I,e ability to clean whilst lubricate etc. No other testing to date comes close to providing such a complete picture of a lubricants performance.

The Holy Grail Lube

Lubes are big business – every cyclist needs one – and they are all vying for your \$. Some lubes are excellent, some are fine, some are rubbish – and it is simply impossible to tell what is what based on drip lubes type (ptfe, ceramic, wax based, nano based, dry, wet, oil etc), manufacturer claims or price.

But choosing the right lube for the right purpose not only gives you back the easiest free watts available – it also saves you lots of \$ in drivetrain wear – especially so if you run group sets at the top of each brands hierarchy. It is like double free speed!

The holy grail is to find a drip lube that matches the performance of immersive waxing in the convenience of a drip lube. Many that have purchased Friction Facts testing have mistaken the performance results of the top performing drip lubes. They will think ah look at that – almost as fast as Molten Speed Wax but all I have to do is drip it on! But the reality is – (as far as we know at time of writing), is that all drip lubes start gathering contamination from km zero. You can ride 100km and your drip lube will be black. You can ride 50km on your indoor trainer and your drip lube will be black. You didn't put a black drip lube on – the fact it goes black so quickly is a hint as to what is happening even just from airborne dust.

So drip lubes that test close to waxing performance on a perfectly clean chain in a lab will be unlikely to test near that friction level after 300km of riding. It will certainly not be remotely near that friction level after 3000km ***(In FF simulated longevity testing –some drip lubes increased by up to 3.8w friction in 1 hour!)***.

Also – in the FF testing the lubricants were applied ultrasonically, with chains fully immersed in the lubricant, at a nice warm 38dg Celsius. This is not representative of how most cyclists apply their lubricants at home. This method ensures complete lubrication of all internal parts of the chain from the first articulation. However as we have seen in our testing - especially with higher viscosity lubricants – it can take some time for them to properly penetrate through to the pin leading to poor performance for the first 1000km or so , after which time there may be good penetration but there may also now be a reasonable amount of contamination gathered slowing things down.

All up – there are numerous aspects that impact the real world friction result a lube delivers vs the FF lab test results.

To remain anywhere near the friction level tested in the lab generally requires chain to be frequently removed and given many agitated solvent baths to reset contamination levels as best as possible back to near zero, and depending on the viscosity of the lubricant – a fairly involved process may be required to ensure proper lubrication of the pin and inside of inner plate shoulders (*refer lubrication gap section*). You also need to clean all the black mess off your chain rings, cassette and jockey wheels.

This is quite time consuming, costly, and you end up with a lot of solvent to dispose of somehow. But to date – we just have not seen evidence that a liquid lubricant can remain near its lab *performance (although we have very high hopes for a couple of lubes coming up on test – whereby this section will be amended)*.

All liquid lubes quickly become contaminated, and many manufacturers claims re abilities to ***“clean as it lubes”*** and ***“form protective membranes”*** is not strong past a certain number of km’s. Intervention with proper cleaning is usually necessary to reset the contamination in the chain, and a protective film can only protect chain metal for so long against contamination particles abrading against it under high pressure. In a part performing around 20,000 articulations a minute on the large chain ring, it doesn’t take too long until the sheer number of articulations hits millions upon millions. A film / membrane can only withstand a finite amount of abrasion before it is worn through and wear

of hardened steel parts of chain commences. In a part working so hard, it only takes a little bit of contamination to have big impact on the level of friction losses and wear in the chain.

Which is why waxing is the tough benchmark to beat. Each re lube (re wax) is fully immersive, at around 90dg Celsius. All parts of the chain are fully coated a very slippery lubricating wax. The remaining old wax layer is melted out into the pot and fresh wax is flushed through so each re wax the contamination levels are reset back close to zero again. Forget protective membranes – every part of the chain inside and out is fully coated with a lubricant which sets solid - preventing metal on metal contact and wear. And with wax setting to an actual solid (almost all dry drip lubes do not actually go dry – just tacky) the rate of gathering contamination and the final amount gathered is extremely low vs drip lubes. When contamination contacts a liquid or tacky surface it sticks. With a solid wax, the vast majority literally just bounces off. And forget a relatively small amount of lubricant being left behind after a drip lubes carrier fluid evaporates– again the entire chain is coated with 100% lubricant.



So that is the challenge drip lubes have to try to match the outright fastest ever tested lubes of Molten Speed Wax & Ceramic Speed UFO wax. Being solid its friction performance barely shifts from the lab test performance for around 300km in normal road conditions ***(in fact it can often decrease by ¼ to ½ a watt as the wax continues to “break in”)***. For day to day riding and training - with each re wax re-setting any teeny contamination levels in the chain without any cleaning required, plus putting a refreshed solid coating on every part which prevents metal to metal contact and wear – we have three distinct factors that deliver simply astounding chain and cassette wear longevity rates. Most prospective new waxee’s don’t believe the wear rates quoted until they experience them first hand. (And of course being a proper solid – waxing is exceptionally clean).

There are some drip lubes that would remain close to their lab test levels for “X” km each re-lube if the chain is fully solvent cleaned between each lube, but not usually where more lube is simply dripped on time after time. I am expecting a couple of exceptions to this rule shortly but be prepared to pay BIG \$.

So is waxing simply unbeatable? Not quite. Despite the entire chain being coated in lubrication, the superfast type of wax used (highly refined paraffin blended with PTFE and Molybdenum) has a relatively short lifespan. Highly refined paraffin has a very low mineral oil content at around 0.5%. The wax is soft and will itself be abraded off the chain through use and from any contamination that does get into chain. It is not water soluble so it does not “wash” off easily, however in tough conditions the water being hosed onto a chain from the front wheel is full of grit, and so the wax itself will be abraded off simply from the countless articulations performed in the wet abrasive substance thrown onto it. Harsh conditions shorten the lifespan of all lubricants – solid wax is no different.

The advantage of the wax is that it absorbs contamination from harsh conditions at a very low rate vs liquids. Initially its very low friction performance remains pretty much unperturbed. The disadvantage is that the wax will itself be abraded off relatively quickly and once it is gone

friction will increase quickly and dramatically. So if you have a long wet race or enduro etc – it may not survive to the end. Remember of course that all lubricants lifespans are shortened dramatically in harsh conditions. So whatever film or membrane or lubrication vector other lubricants have will also be abraded off much more quickly vs good conditions. The difference with drip lubes is that the liquid itself is lubricating and so as long as some liquid remains there is some level of lubrication. The downside is that the liquid will itself have grabbed and held a lot of abrasive particles, so it is part lubricant, part liquid sandpaper. It is common for a chain and cassette to be pretty much destroyed at the end of a 24hr mtb race – whereas in normal riding training and re lubing one does not go through a chain and cassette every 24hrs.

So it can be a bit of a paradox – to start with waxing will be super low friction and resist increasing in friction for an impressive period, but then once gone there will be a large jump in friction. Will this work out better overall than a lubricant that will start higher friction, increase in friction notably and quickly as it becomes a bit of a liquid sandpaper – but then hold at that level for many hours? Is it better to be at 4w friction for “X” time but finish the latter part of race at 15 to 20w, or start at 5 to 8w, very quickly get to 10 to 12w – but remain in that ballpark for many hours? The length of the event and conditions will determine whether it is best to go flag to flag with wax, start with wax and re lube, or go flag to flag with an extreme conditions lube if stopping to re lube is not preferable.

So there will be events where a long lasting drip lube may be preferable to waxing overall due to its longevity – But what drip lubes perform best here? Can’t wait to find them.

And of course waxing – despite being a smart choice for many who initially didn’t know there was another option to drip lubes – will never be for everyone. For a lot of people there is a mental block re removing chain to put in pot of melted wax. Removing chain to solvent clean seems perfectly normal however, and so mass market will likely always want something to drip on and either periodically clean, or never clean – and look for what delivers the best results for their level of application and maintenance comfort.

Lastly - since the FF testing there have been some exciting new lubricants out with some exciting new tech and making some very big claims indeed. Some honestly I can say already will likely be hogwash, but excitingly some others look to be very very good. I can't wait to test and see. I hope to find some bona fide great product options to our stock line up.

And so here we are.... 😊

Below is all optional reading – the more you read – the more you will understand about your chain, lube choices, manufacturer claims vs reality, and how to easily save some great watts AND \$\$ at the same time - especially for those who race, do sportif's / gran fondo's. There will also be some links to a couple of the best articles one should read to fully understand about chain friction and this testing.

So let's kick off - Enjoy!

About chain wear in general

Chain wear is usually measured via chain elongation or “stretch”. The plates of the chain are not stretched longer, however wear of the chains parts – mostly the pins being worn thinner and the bore of the inner plate links being worn larger, means that each link can be pulled a little longer than when it is new.

Measuring chain wear accurately is surprisingly complicated and often not correctly or accurately. The generally accepted “most accurate” is to hang the chain and measure total elongation vs new – and this will give an accurate chain elongation wear measure. The problem is that rather annoyingly chains wear at different rates in different sections – and the difference from one section to another can be quite large indeed. An elongation measure taken across the entire chain will not this up – and if one section of chain is notably more worn than the average wear the elongation measure shows – the section with larger elongation is still going to cause accelerated wear of cassette and chain ring teeth. So replacing one chain at 0.75% wear one time may have a rider fine to run a new chain on same cassette, and another time the cassette may be badly worn and not accept a new chain despite replacing chain at same wear measure.

Measuring multiple sections from centre of pin to pin with a digital caliper is a better way to measure chain – so long as one is very accurate with lining up two centres of pins – tiny fractions of a mm = a large difference in wear rate calculated – and multiple sections of chain need to be checked for an average result, and even tension in the chain needs to be applied. Unfortunately some lubricants that are fairly viscous and / or if a lot of contamination is built up in the chain – this can easily prevent pins from being pulled to their true wear mark as gritty lubricant is filling the gap. Under rider load however the pin will be pulled through this – and so it can be easy with some lubricants to give falsely very low wear rates using pin to pin measuring – and again to be accurate one needs laser eyes and a steady hand to get multiple true centre to centre of pin measures across a good span of say 10 links to calculate wear.

So making it easier – sort of – are a whole array of chain wear checkers, some are drop in, some are slide in, some try to isolate roller wear from the equation. If you read some forums you will often find engineers of some degree or another denouncing chain wear checkers as a huge waste of money, flawed etc – just use a ruler / digital calliper. And yes the issue with most chain wear checkers is that at the two insertion points the checker will also be measuring wear of the inside of the roller bore and wear of the outside of the inner plate shoulders that articulate inside the roller. These two areas of wear have no impact on chain “stretch” or elongation. Some checkers are designed to isolate this wear from its measures.

So, yes – many chain wear checkers are going to measure two types of wear at two points on the chain, and just elongation across the rest of the span it is checking. One can only hope that the manufacturer of the checker took this into account when calibrating their tool. What these checkers do provide however is a quick and easy way to check multiple spans of the chain, and if used correctly can be a cyclists best friend re saving a fortune on not having to replace cassettes every time they replace their chain.

Where these fall down is often in two parts;

- 1) Most are too generous re wear allowance – by 1.0 the chain is ruined and so will have already ruined your cassette and had a good crack at your chain rings. Even by 0.75 measure it is touch and go, and you can be almost guaranteed that if one section of chain measures 0.75, another section will be around 0.9 – and so can still easily result in goodbye cassette.

- 2) They are very susceptible to the amount of user pressure applied, and need a consistent tension in the chain. If one checks the chain above the chain stay with little to no tension in chain, or check chain beneath chain stay in “X” gear which will put “X” amount of tension in bottom span of chain from derailleur pulley can easily get highly varying results. With chain wear measuring we are measuring small fractions of a mm, so differences in user pressure and chain tension can easily have one person check a chain and say it is almost new, and another person check same span and say it needs replacing. And again some lubes will mask the true elongation wear unless a lot of tension is put into section of chain prior to measuring, whereas others require very little tension to reveal an accurate elongation wear measure. For my two cents worth, the Park Tool cc3.2 is the best analogue checker, it is a drop in checker with a 0.5 wear measure mark which is perfect – used correctly I have never ever had a time where a cassette does not accept a new chain when the existing chain is replaced at 0.5 wear mark. A conservative chain wear checker is not a conspiracy theory tool to have you buying chains more often than you need – it is your best friend to save you a fortune over time in cassette and chain ring wear. (And worn chains perform like crap – a 1% worn chain will be around 2w higher friction than same chain new – even when perfectly cleaned and re lubed).


It is also worth noting that the wearing of the inside of the rollers and the outside of inner plate shoulders is still actual wear and it still contributes to a chains performance and damage to cassettes and chain rings. Some lubricants can be quite good at preventing contamination getting through tiny gap to the pins and so have a relatively good rate of elongation wear, but have gritty liquid sandpaper running inside rollers. I have seen many chains where elongation wear was not terrible but rollers were flopping about all over the place and could be shifted millimetres to the left or right. So isolating chain elongation wear only is not the be all and end all it is cracked up to be. Ideally there would be a tool that accurately measured elongation AND roller wear easily across a span of links vs trying to isolate wear measuring of elongation only – but this tool hasn’t been invented yet.

And very importantly, - chain wear and friction is not a linear increase over time. Good quality chains come with a low friction coating, and the better ones have something like a Zinc Alloy or Nickel or Ti Nitride plating on inner and outer plates, and even better chains have specific very hard coatings on pins and rollers such as chromium carbide. These coatings and platings play a big part in a chains friction performance and durability – but they are also the first to be compromised from abrasive wear. With many drip lubes this can occur frighteningly quickly. It is part of why world tour teams tend to replace their chains every 500 to 1000km. As the coatings / platings become compromised, friction and

wear rates increase. Also, without regular proper cleaning for most drip lubes the ratio of contamination vs lubricant inside the chain will generally continue to get worse and worse. As such a chain subjected to the exact same level of load and conditions will usually exhibit a higher friction and wear rate between say 2000 to 3000km than it would have from 0 to 1000km. Most times there is the double whammy of lubricant is now more contaminated, and protective coatings / platings no longer exist (*take for example the Rock n roll gold test – wear rate for 0 to 1000km was 8.9%. From 2000 to 3000km which was again a clean block with no added contamination it was 20%*).

This often catches cyclists out. A cyclist may check wear at 2000km and be impressed with low rate of wear. Check again at 4000km and find it has ripped past the 0.75 mark and now they need a new cassette as well as the chain. Most annoying.

It is also a key reason why we recommend cyclists who race or compete in sportif's / gran fondo's etc have a dedicated race chain and training chain. It is the easiest and cheapest watts savings you can get. You are always going to need another chain – so simply pre buying your next chain has a zero net cost. When training chain reaches 0.5 wear replacement mark – race chain becomes training chain, buy another chain to be your race chain.

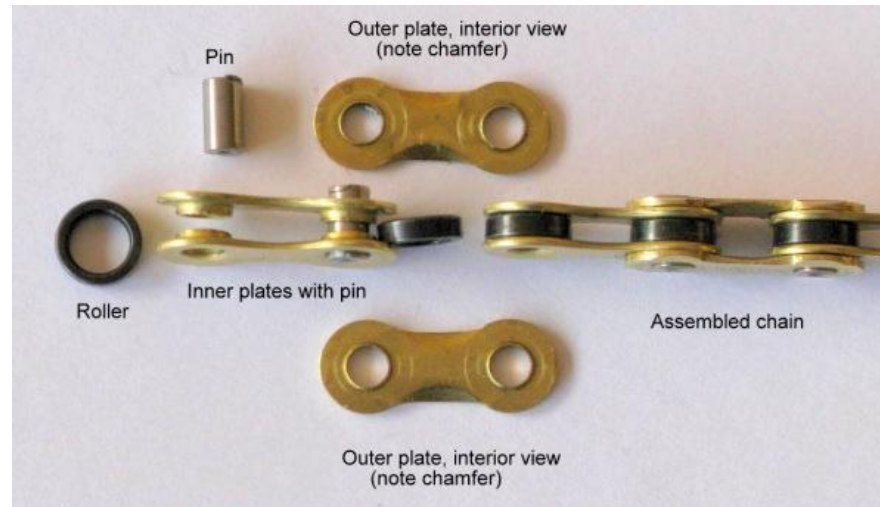

(Pic sourced from slowtwitch)

Did you know? - When a chains roller contacts chain ring / cassette teeth etc, the roller stops moving and the inner link plates articulate inside the roller. The pin is also riveted in place to the outer plates so it doesn't move either – the inner link plates articulate around the pin. Therefore as the link articulates, the inner plates are the only rotating parts; however there are multiple friction and wear interfaces;

- The inner plates will articulate around the pin on the inside bore of plate shoulders (those flanges you can see that the roller sits on) under full pedalling load.
- The outside of the plate shoulders articulate inside the roller under full pedalling load.
- The inner plate slides against the outer plate on both sides of the link – the pressure under which it is doing this is dependant on both rider load + chain line angle.
- The inside of the inner plate sides slide against the sides of the roller – again the pressure under which it is doing so dependant on both rider load + chain line angle.

- Chain wear occurs from the pin being worn thinner, the inside bore of the inner plate shoulders being worn larger, the outside of the plate shoulders being worn thinner from articulating against the roller, and subsequently the bore of the roller is being worn larger. As these parts wear down, each link can be pulled slightly longer than when it was new, and rollers can start to flop around on inner link shoulders.
- The wear of the inner plate against outer plate and sides of the inner plate against side of rollers does contribute to friction, but does not contribute to “chain stretch”. The loads here are much lower than the full rider load which causes chain elongation wear. Over time – especially for those who with large chain angles a lot – a condition known as “chain slap” may develop where the chain becomes a bit too laterally flexible resulting in poor shifting performance. Deraileur chains do need to be laterally flexible, but there is a sweet spot.

Up to 0.5mm across 8 links is very close to 0.5% wear on a 108 link chain, and this is the best limit to use as a guide to replace chain as it is getting to the maximum tolerance of the spacing of your cassette & chain ring teeth. Stay within tolerance and the rollers will slot neatly into the teeth without abrading their way down the face of each tooth. Let chains get to 0.75 and the rollers are starting to hit the tips of each tooth first before being forced to sliding down the face. By 1.0 – things are getting pretty bad – the more chain stretch the more your chain is rapidly eating all your teeth thinner.

And not surprisingly, having your chain eating through the metal teeth on your cassette and chain rings is not exactly low friction either. It should not come as a shock that abrading through metal whilst pedalling along eats up watts as well as \$ from your bank account.

So, replace chains at 0.5, and save a bunch of watts and cash, and have a beautiful running drive train. It is also a lot safer. A worn chain is much more likely to fail – with very thin chains and greater chain line angles of 10, 11 and 12 speed drive trains, running clapped out chains greatly increases chance of failure. This can have you over the handlebars in a sprint and bringing down a pack, or if your chain goes into back wheel it can cause a spectacular amount of damage to bike and frame as it rips your rear derailleur from frame and into back wheel etc. In summary – your chain is your hardest working mechanical part, and running completely exposed dust and the elements. This makes it a highly consumable part – stay on top of chain wear for watts, \$\$, the silky smooth pleasure of not riding a clapped out drivetrain, and safety.



(New vs worn chain ring teeth. The exact same thing happens with your cassette teeth only much faster. Abrading away metal is not low friction. Replace chains at 0.5 and your chain rings will last almost indefinitely, and you will always get 2, often 3 chains per cassette. Let run too long and it is almost always new cassette time when it's new chain time, and can also easily lead to new chain ring time too. This is a very expensive way to run your bike vs simply replacing chain when it should be replaced.

The lubrication GAP!!

There are three critical area's to ensure lubrication for the chain as it articulates under load. The two most important areas are;


- 1) Between the roller and the outside of the inner plate shoulders as they will rotating inside the roller under full rider load.
- 2) Between the pin and the inside of the inner plate shoulders. It is wear of the pin and inside bore of the inner plate shoulders that is measured with chain elongation wear measuring. These two interfaces are also articulating under full rider load.

The last place that needs to be lubricated is between the inner and outer plates on both sides of the link as they will slide against each other as the link articulates, however when chain line is straight there is very little load here – it increases as chain line angles increase (and similarly there is friction between side of the roller and side of the inner plate which will come into play more at greater chain line angles).

In general lubricants will not have too much trouble penetrating and lubricating between roller and outside of inner plate shoulders or between the inner and outer plates interface, side of rollers and inner plate interface.


The trickiest part is to get lubrication into the other extremely important area under high pressure friction load – the pin and inside of the inner plate shoulders. Access to get into here is very limited now that chains have become super narrow as demonstrated by image below.

Pin is riveted to outer plates & does not move. Inner plate articulates around pin. When roller contacts teeth roller stops, and so inner plate also articulates inside roller.

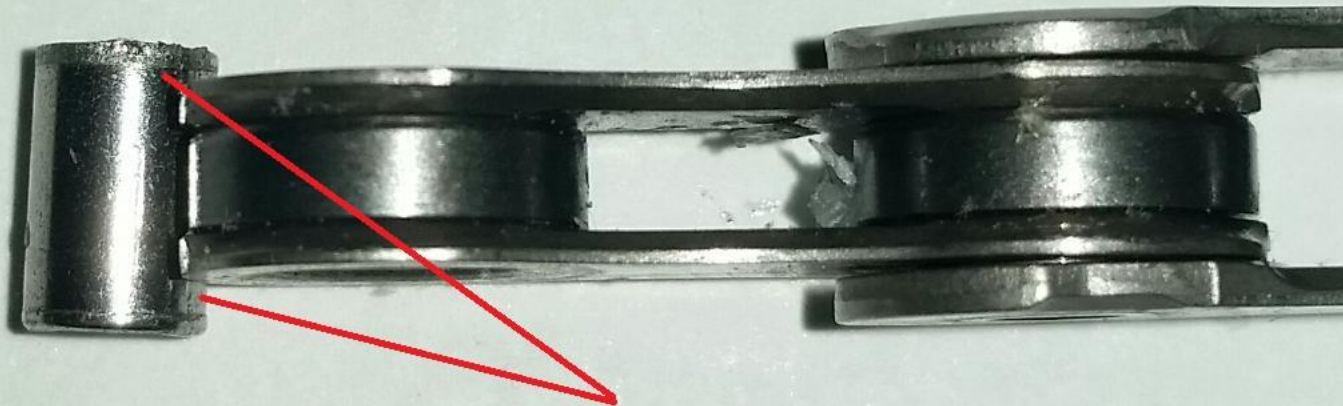

Note amount of pin width that requires lubrication - inner plate shoulders articulate around this area under full rider load.

Note lubrication gap through which lubricant must penetrate & disseminate across pin width. Any contamination gathered by lubricant also needs to get back out of this gap, and back out past roller to outside of the chain.... Tricky

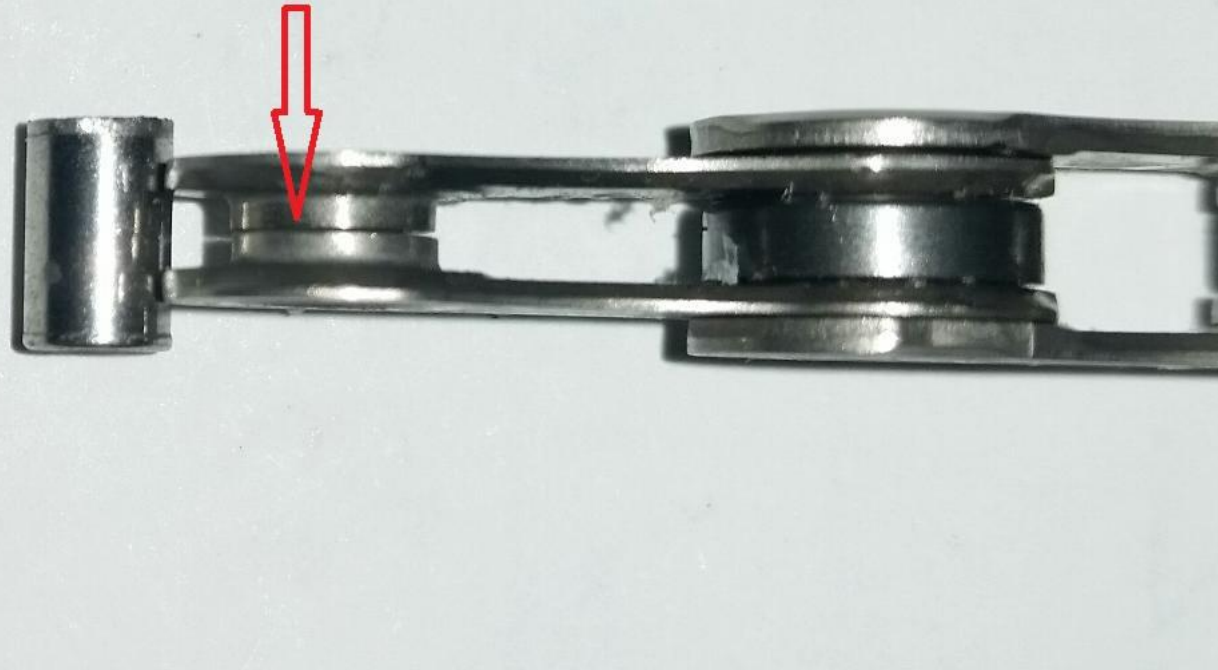

Not all chains are the same here – some chains will have thinner plate shoulders and a larger lubrication gap, some will have wider plate shoulders and a very narrow lubrication gap. Thin lubricants will generally not have too much issue penetrating across pin quite quickly, however more heavily viscous lubricants most definitely can.

Note chamfer on outer plate. This prevents lubrication from also being able to access pin via gap between inner & outer plates, leaving the small gap underneath roller as the only lubrication gap access to pin.



As we discovered with testing for some of the top wax emulsion drip lubes with Squirt and Smoove – the importance of this lubrication gap was demonstrated very well with initial block 1 wear rates vastly higher than expected, and then showing an improvement trend - in Smooves case the improvement as km's went on was very stark indeed – showing only 2% wear from 2000 to 3000km block vs a 19.1% wear rate from 0 to 1000km. This is the opposite of what normally occurs with drip lubes without regular cleaning maintenance whereby as the contamination to lubricant ratio continues to increase – so does wear rates so the block 3 wear for most drip lubes will be much higher than block 1 because more contamination is running in the chain and any chain platings / coatings have been compromised.

However with certain lubes such as viscous wax emulsion lubes – the opposite effect was seen as over time and many re lubes more of the viscous wax was able to penetrate to through this lubrication gap to get to where it is needed build up layers of lubricating wax.

As such one will see in the reviews for Squirt and Smoove a recommended technique for initial lubrications after cleaning chain of factory grease that is **much** more involved than the manufacturer instructions which yielded very high block 1 wear rates due to lack of lubricant penetration through this gap.

This gap is also important to take into account as we move to covering other common manufacturing claims such as forming clean protective membrane on chain to prevent metal on metal / contamination on metal contact, as well as cleaning as it lubes by shifting contamination to the outside of the chain leaving just clean lube inside the chain. Both are a tricky promise to deliver on.

So let us ponder this challenge a little bit. Take your current chain and run your hand or cloth along it. You get a lot of black contaminated lube on your hand / cloth. If you were to completely clean the outside of the chain so that it looked brand new, and then take chain off and put in a container of solvent and give it a shake – the solvent would instantly turn black from the black contaminated lube running inside the chain that is now flushed out.

So when you add fresh lube, this liquid is running through all this black contaminated lube on its way to the inner workings of your chain. And if most manufacturer claims are to be believed – it is apparently doing so without getting contaminated itself, penetrates through this very narrow channel to lubricate the pin without bringing any contamination in with it, shift any contamination that is in there back out of this very narrow channel, and then shifting it to the outside of the chain. And after having achieved those feats it then leaves a nice clean film / membrane of lubricant behind protecting chain metal from contamination abrading against it causing wear / prevent metal on metal contact.

Tall orders. All of them.

The level at which a lubricant does or does not achieve these claims has a very large impact on chain friction and wear once the lubricant leaves the lab and has to contend with contamination. Different lubricants grab and hold contamination at different rates. Different lubes penetrate the lubrication gap to pin without difficulty or with great difficulty. They have differing abilities to shift contamination from inside chain back outside again. They form differing strengths of any protective films / membranes. The combination of all these factors and many more will determine a lube's day to day performance in the real world, how close it remains to its lab performance and for how long, how much maintenance / intervention is required to keep it performing well, and what conditions it can or cannot handle.

So far our proper longevity testing has delivered some important learnings in this area vs short lab testing.

- 1) Highly viscous lubricants such as wax emulsion lubes (Squirt / Smoove) when applying to a chain stripped clean of factory grease, I would recommend re lubing very frequently early – after every ride – for at least the first 5 rides to ensure sufficient penetration through the very narrow lubrication gap to the pin and for it to begin to build up lubrication on the pin. Try to ensure applying whilst lube is warm and chain warm (i.e indoors vs outdoors in winter). Don't worry about that you will build up tacky stuff on the outside of chain and drive train more quickly - you can clean the outside of the drivetrain as you need. After this initial lube rate you should then move to normal manufacturer recommended re lube rate – just keep ensuring lube and chain warm for application and thoroughly work in with lots of back pedalling in small cogs whilst wet after applying.

*(*If I was preparing a chain for a big event like a 12 or 24hr mtb race or long gran fondo like 3 peaks – I would follow the detailed prep instructions as outlined in detail reviews for those lubes. One lube in particular has demonstrated it effectively “Layers”, so allowing each application to thoroughly dry after taking pains to work into chain whilst still wet, and repeating to add another “layer” – has shown to be effective with Smoove – but that is the only lube seen to date where this is the case).*

- 2) For normal / light viscosity lubes – the concern is not about penetration through this gap – but more so regarding how much abrasive contamination it brings in with it on its way through, and how does it get contamination back out through this gap and leave behind clean film / membrane only? So when prepping a chain here it is simply ensuring a proper clean first, then thorough lube whilst articulating chain around drive train, and thoroughly wiping excess. Repeatedly adding more and more lube - as recommended to ensure penetration with highly viscous lubricants - is not recommended here. Penetration is not a concern and excess lube is simply going to gather more contamination. Properly clean, thoroughly lube, wipe excess , let dry if specified – prep done.

About Chain Break in!

There will be a surprising amount of metal particles released when you first ride a chain – left over from the manufacturing process. The factory grease is quite good at absorbing these metal particles, and also forming an initial level of smoothing / polishing the metal surfaces. There is a nice little butter zone here to set a chain up well for its future performance, a bit like a proper break in for a new engine.

Too often cyclists buy a new chain, ride the factory grease until its getting dry, then start adding drip lube. Aside from the fact that the drip lube will be highly tainted by the factory grease and unlikely to be able to perform as designed (bond to metal surface, form lubricating protective film / membrane etc), but also without proper clean post a couple of initial runs – you are going to be leaving a lot of metal particles running in your lubricant. These particles are – like your chain – made from hardened steel.

So in the same way you wouldn't tend to sprinkle hardened steel particles on you chain for fear of greatly increasing friction and wear, one should also look to remove hardened steel particles after an initial 1 to 2 hours of riding with factory grease.

Friction Facts have tested that even a rudimentary break in such as the above will reduce chain friction by around 0.5w, and this will carry forward for the chains performance once cleaned and lubed with your lube of choice. You will find that all race prepped chains have had an initial break in with factory grease prior to ultrasonic cleaning (if a company is making race chains without an initial break in, they are short cutting a very important step.

You can see from the images below the amount of metal that initially comes out, and so left in after an initial break in is likely to start causing premature wear and damage – especially to the special plating and coatings your chain main have depending on the level of quality of your chain.

- Note for waxing customers – if purchased a pre clean and waxed chain then a nice amount comes out from the many rounds of ultrasonic cleaning, and the remained will come out over time as you re-wax. This does mean it is going into your wax, but you will still have vastly less metal particles running in your chain vs those adding drip lube on to factory grease.
- There is now an option to purchase chains that have been broken in , ultrasonic cleaned and waxed, as mid price option between a clean and wax and a fully optimised race chain.
- However if you want to save your \$, you now know what to do with your new chain at home. Ride for 1-2 hours with factory grease in clean conditions – fully solvent clean with agitated solvent baths, always finish with methylated spirits to ensure no film left from degreaser or similar so that new lube has direct access to chain metal, and away you go.





About having a dedicated race / A chain

So as discussed - your chain is a very consumable item. Sooner or later you are always going to need another chain, and for those that race or do sportif's / gran fondo's and so tend to clock up some training miles, needing a new chain is never too far away – especially if replacing at recommended 0.5 wear mark.

It doesn't cost any more to simply pre-buy your next chain and have a dedicated race chain. This chain you break in with around 100km of riding with factory lube, remove and fully solvent clean, lube as per instructions with your chosen race lube, and keep it wrapped in cloth ready for next race. Properly clean and re-lube after each event to keep it mint. Most especially so if using drip lubes - this will give you some of the cheapest and easiest watts savings you can get. Versus racing on the same chain you use in training that will be contaminated, compromised coatings / platings, some level of wear – you can expect to save at least around 3w @ 250w load, possibly quite a lot more, and with this figure nearly doubling by 500w, nearly triple at 750w (power climbs, attacks etc) as chain friction increases at an almost linear rate to rider load.

When your training chain reaches 0.5 wear, your race chain moves across to become your new training chain, get new chain to become dedicated race chain – break in, clean and lube with your chosen race lube. This method is simply one of the smartest, easiest and cheapest ways to save a bunch more watts than you will with very expensive bearing upgrades – and it will save you money on drive train parts by having them last a lot longer. Double free watts!

There are also numerous options to buy a pre prepped racing chain to skip the above hoohaa, and then all you need to do is the keeping it mint part.

**Note - New chains will decrease in friction by around 0.5 to 1w after being "Broken in". Break in your new race chain by riding for around 100km in clean conditions and then properly clean – ensuring flush out ALL the contamination you can. If it is not properly cleaned – friction losses from contamination will undo the friction gains from break in.*

Ok – onto manufacturers claims!

Forms a protective film / membrane

This is the big one. A lubricants ability or lack thereof to form a film / membrane to protect the chain metal from either metal to metal contact under rider load, or abrasive contact from contamination on chain metal under load - will have a huge impact on chain lifespan and real world friction performance. This is a big part of what can separate those with a good lab performance but poor performance outside of clean chain clean lab testing and those that remain close to lab test results for an impressive period of time.

Almost all lubricants claim to form a high strength film / membrane that protects chain from metal to metal contact & contamination to metal contact – both of which cause high friction wear to a chains hardened steel parts. And there is huge variance in the industry regarding which lubricants do this well as per claims and which do not.

The challenge of achieving this well with a drip lube is substantial. Initially – assuming one has properly cleaned chain and applied lube as per instructions – it is likely that if a manufacturer is claiming this property for their lubricant – it is doing so. But how well...

The variances come into play with;

- A) How strong is this protective film / membrane – can it prevent metal to metal contact / contamination to metal contact under high power rider load?
- B) How long can this protective film / membrane last against the abrasive assault from contamination?
- C) Part B may be determined by how much and how quickly the lubricant gathers contamination, as this will determine the level of abrasive assault being mounted against the film / membrane.

There can tend to be two stereotypical scenario's;

- 1) A light bodied drip lube which may go semi dry and have a lower amount of contamination gathered to abrade against film / membrane. However the film / membrane formed may not be strong enough to prevent metal to metal contact under rider load, and it may be worn through quite quickly even from the relatively small amount of abrasive contamination gathered.
- 2) Or it may be a heavier / wet lube that may form a stronger film / membrane – however wetter lubes also tend to gather more contamination more quickly. A stronger film / membrane will resist metal to metal or contamination on metal contact at higher loads, however if it is under assault from a veritable battalion of gathered contamination – it may still be abraded away in short order.

The best possible scenario is a lubricant that has a very strong layer of protection against metal to metal & contamination to metal contact under load, and that also gathers a very low amount of contamination very slowly. Unsurprisingly immersive waxing is extremely hard to beat here – every surface of the chain metal is protected with a completely solid layer of lubricant vs the very thin film / membrane from a liquid. And being completely dry and solid it gathers extremely little contamination – most literally just bounces off. Whereas with the exception of the Ceramic Speed UFO drip lubes, other “dry” lubes do not go truly dry – either less wet, or very tacky. The abrasive assault against the wax layer is typically very low compared to what the liquid film / membranes need to contend with.

The other extremely important aspect to consider is what is happening when you are re-applying your drip lube. Few riders are going to fully clean their chain after every ride, or even perform frequent proper maintenance with a full flush clean every 1000 to 1500km.

So the drip lube is added to a chain full of black contaminated lube, upon which the lubricant needs to pass through all this without becoming contaminated itself and form a new clean protective membrane between the contamination and the chain metal. Honestly that is some feat. The fact that the majority of chains on drip lubes will hit 0.5 wear mark within 3000 to 6000km speaks to the general level of success here I think – the hardened steel parts of your chain are still being abraded through – if a membrane was preventing metal to metal contact or abrasive particles contacting metal and the links were articulating just on a nice clean membrane – the links would not wear.

At the time of writing – I find this claim to be a stretch for most lubricants. I think many form a decent film / membrane when applied to a clean chain and that this membrane will reduce friction and wear for a while. However just adding more lube on and expecting a nice new clean film to form despite chain being contaminated takes a bit of faith, and I expect any new film / membrane to hold up for lesser and lesser time as contamination assault against it continues to build.

This is demonstrated well in our testing by much higher wear rates in subsequent clean blocks during the test vs the lubricants clean block 1 wear rate (in most cases – but not all 😊). The usual continual acceleration of wear is an indication re how well this claim is being executed.


So – in summary – almost all lubes will claim to do the above – but in practice how well they actually achieve this aspect will have a huge bearing on their real world friction and wear performance – and the level to which the lubricant performs here is be uncovered in our longevity testing, and not usually revealed too well in lab testing.

The below is from Bike Mechanic website (makers of bike milk / bike mix / bike syrup) and may help explain what we are talking about re lubricant preventing metal on metal contact. Many thanks to Owen for sharing some great extra knowledge that assisted me in solving the mysterious initial wear rates for Squirt / Smoove – very few people have Owens level of knowledge on chains and lubricants!

MECHANICS OF CHAIN LUBRICATION & EXTREME PRESSURE ADDITIVES

The extreme pressure additives in BIKE SYRUP are designed to coat and bond to the metal surface. This prevents metal-metal contact and reduces noise. It is the fundamental reason the chain runs so quietly.

Lubricant mode of action can be simplified into 2 types: boundary and hydrodynamic. Hydrodynamic lubrication requires a film of liquid to remain in between the two surfaces. Under high pressure loads such as those experienced in between a chain pin and the bushing the liquid lubricant required for hydrodynamic lubrication is squeezed out of the space between the two surfaces and boundary lubrication is required for effective protection.

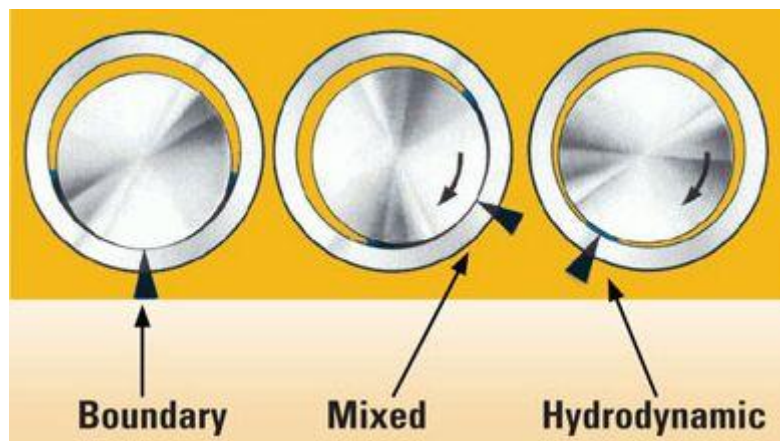

The best boundary lubricants are long chain molecules with an active end group. The active end group attaches itself to the metal surface and gradually builds up a surface layer. The long chains form a layer of lubricant which separates the metal surfaces and there is no direct contact of the sliding parts. This situation is required for many extreme pressure applications to prevent severe wear or high coefficients of friction and seizure

Drip lube “Cleans as it Lubes” claims.

This is the next big one. Again just about all lubricants claim to do this - and there are various methods via which lubricants claim they achieve this feat.

Firstly let us look at the manufacturer claim for one of the lubes tested so far – Rock n roll gold;

“The formulation goes deep down into the chain and traps any dirt. Then, with the energy of the chain freewheeling backwards, the dirt and grit floats to the surface so you can wipe it all off, leaving a new and clean application of lube inside the chain, where it’s needed. The lube down inside the chain creates a protective membrane to seal out dirt and moisture from the moving parts of the chain. As well as holding in place the best lube on the planet, for longer chain life, super smooth shifting and pedalling”

And yet during the test, the wear rate in block 3 which had no added contamination was over double the wear rate for block 1 which started on a clean chain. When the chain was properly cleaned after main test for the single application longevity test, the wear rate for the first 250km was reset be extremely similar again to the wear rate recorded in clean Block 1. In short – properly cleaning the chain removed a heck of a lot of contamination that the re lubing didn’t. Rock n Gold did perform some level of cleaning as the wear rate reduced by nearly a third on block 2 wear rate which had added contamination – so their claims are not all hyperbole – but it is up to you as the consumer to decide if “less dirty” can be classed as “clean”, and if the level of cleanliness achieved matched your expectations after having read what the manufacturer has advised it would do.

So drizzling on a lot of new lube and wiping away excess may perform a level of cleaning. But it may be quite small.

When I properly clean a customer’s chain it takes around 10 x 200ml agitated solvent baths to flush chain clean. The first bath goes instantly black. The second bath goes instantly black. And again, and again. After about 1 litre it is now starting to turn grey, then lighter grey, until finally around 2 litres later the mineral turps comes out similarly clean vs how it went in. The amount of particulate contamination captured when I pour the turps through paper towel as I go is huge. You can obviously easily test this yourself with your current chain at home! So – just how much contamination can really be flushed out with about 10ml of a lubricant across 108 links is worth pondering. I find these claims

akin to the following analogy - Think of a sink full of dirty water from washing a pile of greasy dirty dishes. Imagine turning the tap on for 1 second whilst simultaneously pulling the plug for 1 second. Is the water in your sink now clean?



(Solvent clean of Rock n Roll gold after 3540km. 2 litres of mineral turps before it was coming out similarly clear to when it went in. So, was RNR gold cleaning as it lubed? You can see what is running inside the chain along with any new lubricant that is added, and you can imagine the task for the lubricant to form a new clean film between contamination in the chain and the chain metal. And if it does achieve that feat, how long can said film last against such an abrasive assault? It is also worth noting Rock n Roll gold is one of the better performing lubes, what is happening with lubes that achieve claims to a lesser degree?

Use of sandy loam as our contamination also really highlighted what happens when more lube is applied / chain wiped during re lube. Sandy loam will crunch away very audibly when it penetrates inside the chain. After running for a while, this crunching / grinding sound stops as now the worst of it has now either been ground to dust or it has been worked to the outside of the chain. However when lubricant is added again at next re-lube interval – the crunching and grinding sound immediately recommences. This proved a long held concern - drip lubes are applied on the outside and work their way in, as such they risk bringing contamination sitting on the outside of the chain back in with it. If one was to carefully apply a small drop directly onto roller – this seems to minimise this occurring, however lubes that want you to drizzle on whilst back pedalling and then wipe chain clean – there is a big pick up in crunching going on inside chain after each re-lube. So during re lubes – yes fresh lube is being added, and yes to a very very small degree the total level of contamination in the chain may be diluted. But things may also get worse for a while before they get better where it really counts – inside the chain. The outside of your chain looking cleaner counts for very little. It is hard to imagine a liquid applied to a contaminated chain won't itself become immediately contaminated on its way through penetrating from outside in. At the time of writing I have not seen a drip lube that is “cleaning as it lubes” to any feasible definition of “clean”. It may make chain look clean on the outside for a while, but pop chain off and give it some solvent baths and you will see what is running as lubricant inside the chain where all the action is happening.

- Lubes that contain solvents – these may help in a couple of ways. If you haven't cleaned your chains factory grease / oil (which tend to grab a lot of contamination), these solvents can help remove factory grease / mineral oils so that more and more you are left with the lubrication you have purchased being what is lubricating your chain. But these solvents are not acid – they are not going to dissolve dust and grit. These lubes can gather less contamination overall and at a slower rate than a mineral oil / factory grease - but the solvents themselves won't “clean” your chain of dust and grit.
- Note - for the vast majority of lubes - removing chain and properly cleaning will deliver a significant reduction in friction and wear, and this is highly recommended to do prior to races / events if you use the same chain for racing as you do in training. However – there are some lubes which focus on building up a lubricating layer inside chain and so do not wish the user to fully clean chain as that will remove lubricating layers built up. The longevity testing has proven this to be correct for these lubes, however I find it would be a big call to say that a very clean chain with a fast lubricant is not going to outperform a chain that has simply been re lubed for “X” hundreds or thousands of km's and will have gathered an amount of contamination. So for those running lubes that require time and layers to build up, I would still highly recommend fully cleaning as contamination always ruins a low friction party, and then follow my more

involved recommendation re building up lubrication layers in a way that keeps contamination gathered to an absolute minimum. The goal always for a race chain is a perfectly clean, perfectly lubricated chain.

- In testing an issue has been discovered with some the drip lubes that go quite dry or become like a “plastic” state. These lubes can resist gathering contamination well during normal dry riding and also in dry off road conditions. However during wet ride conditions, the water provides an easy vector into the chain, however the lube may have no mechanism to shift the contamination back out again. Some dry / wax lubes “shed” – and so use up some of themselves in an attempt to shift contamination back outside the chain – which can provide a small level of cleaning at a cost of longevity for the lube application, however some do not really shed and have simply no way of getting contamination back out. These lubes typically have a frugal application process, so there is no flushing out of contamination either. Lubes of this type can be a bit of a catch 22 as whilst they can be excellent at resisting contamination in the dry, and perform at a comparative high level during a wet ride or event, one can be left with task of fully cleaning chain after wet rides or the contamination hosed in by front wheel is simply going to stay there resulting in high friction and wear for subsequent rides post any wet ride. Compounding this is that some of these lubes can also be quite viscous and take time to properly penetrate through lubrication gap to pin again after chain has been properly cleaned – again leading to either high friction and wear rates for a while post clean, or if wish to avoid that quite a rigorous process post clean to negate this.

DRY LUBES

Most manufacturers know that many customers covet a clean drivetrain with a minimum of hassle & cleaning maintenance. When it comes to dry drip lubes they are attempting to act like a solid lubricant. They are a lubricant (often a type of wax or a blend of multiple types of wax) suspended in a carrier fluid which then evaporates to varying degrees, leaving behind said lubricant. In reality this is not always executed well – very few dry lubes go actually dry – they go sort of less wet and become tacky, and some leave behind very little actual lubrication. As a grouping dry lubes often friction test poorly and can have a frighteningly short lubrication window.



(Lubricant vs carrier fluid. Imagine if you will the amount of actual lubrication left behind each re lube vs other lubricants where the majority of what is being applied is the actual lubricant. You could drizzle half the bottle on, and across 108 links the amount of lubrication per link will still be not much! The above lube tests terribly in every test it has been subjected too)

There are a couple of good exceptions to this rule though where this approach is done very well, with a large of amount of lubrication left behind after carrier fluid evaporates leading to a slower and lower rate of contamination gathering. The best have tested very well for efficiency and longevity, however as a nice paradox these most certainly do not remain clean. In fact one of them built up so much gunk during test I was no longer able to back pedal the drivetrain when reapplying lubricant – so cleaning maintenance for these lubes is high if you want a clean looking drivetrain. Done poorly – and these are often the cleanest looking ones - there can be so little lubrication left behind that quite quickly after each re lube there is simply so much metal / metal and grit / metal contact they deliver very poor friction levels and very high wear rates. And you certainly would not want to be out on a wet ride or you have about 30 minutes of lubrication, after that the water being sprayed onto your chain will be doing the majority of the lubrication! So, some may look cleaner on the outside vs a wet lube, but in a lot of cases the beauty is only skin deep – what is happening inside where it counts can be not great.

So in short - dry lubes done well can be very good, done poorly and they can be pretty shocking.

About “metal conditioning”

There are some lubes (of which we will get around to testing hopefully) that make some other interesting claims re why their lubrication is the best. One of them is that if you were to look at the metal under high magnification you would see that the metal is not perfectly smooth but the surface is covered with fissures, and that their lube fills these fissures to leave a completely smooth surface. I have no grounds to believe their lubes are not actually doing this, or trying to do this, however I speculate that contamination is merrily scratching in new micro fissures every time the link articulates. Which is a lot. I imagine it as something akin to you have a team of people shovelling to fill in trenches, and a team of people right next to them digging trenches. To date I have not seen a lube with this claim test well for outright efficiency, nor seen obviously better longevity rates. One will note this is believed to be different for claims re wax (paraffin, Molten Speed Wax, Ceramic Speed UFO and UFO drip lube) where it has been tested and proven that wax increases in efficiency and decreases in friction whilst being ridden in part due to wax surfaces becoming highly polished so one has two super slippery solid lubrication layers sliding against each other – contamination free. The two conflicting teams of trench fillers / diggers is largely negated as the vast majority of contamination simply bounces straight off the chain, whereas with a liquid lube contamination is immediately absorbed by the liquid and is now able to abrade against whatever surface it is in contact with every articulation.

Another claim under this banner is that they “condition” the actual chain metal by polishing it to a smooth shiny surface. There is a high profile lubricant in particular that claims this, and it did not efficiency test well at all. It may well be polishing away the metal, but that would **have to take friction to do so**. You can’t polish anything with a frictionless substance. So the lubricant basically claims it is performing the duties akin to a very fine emery cloth, and even if it is super fine – it still **MUST** take friction to polish metal. Add a small amount of friction across multiple surface interfaces articulating 20,000 times a minute – and it is not surprising it friction tested right near the bottom of 55 lubes tested. (Again comparing to wax – wax is soft and becomes polished quickly and easily – but the fact friction typically drops by around 0.5w from when it starts the process to when it quickly finishes the process – it is still taking some friction to get from not polished to polished.

Polishing hardened steel – that is also often plated with specific hardened coatings like chromium carbide, titanium nitride, nickel, or a zinc alloy etc - would take somewhat more polishing than wax.

And yet again on this – surely in short order contamination will be scuffing and scratching the surface ceaselessly putting micro scratches back in. Attaining their smooth polished surface would be quite the ongoing tussle.

As yet I am not convinced “metal conditioning” is the best approach re achieving a high performance chain lubricant and I would have concerns paying big \$ for a lube in this category.

About Factory Lube

A common mistake many people tend to make is to just ride factory lube and then start adding their lube of choice on top of that. Factory lube may feel good and smooth, but that’s simply because the chain has been immersively lubricated, is brand new, and so vs the old chain worn out full of grit chain you just took off, it is going to feel good.

But factory lubricants are not really designed to compete with the best chain lubes. Testing shows that in general factory lube tends to range from mediocre performance to frankly terrible. One can 2 to 5w just by cleaning off factory lube and replacing with even a mid pack lube.


Factory lubes also don’t tend to focus too strongly on contamination resistance – most gather a lot very quickly.

So riding your new chain with factory lube and then adding your selected drip lube on top – likely a completely different type of lube which may not mix well – can totally undermine that lube’s ability to perform as per manufacturers claims. You will find a lot of manufacturers do state to apply their lube to a clean chain – but most cyclists either do not clean off factory lube, or perform a very inadequate clean such as wiping the outside / spraying on some degreaser and wiping etc – it takes a lot more than that to properly clean a chain.

****No matter what is your chosen lubricant – always properly clean off factory lube, and give your lube of choice a chance.***

*****However – it is good to ride factory lube to “break in” new chain for 50 to 100km in clean conditions – and then clean factory lube off properly – especially recommend this for prepping race chains.***

Latest Tech Lubes

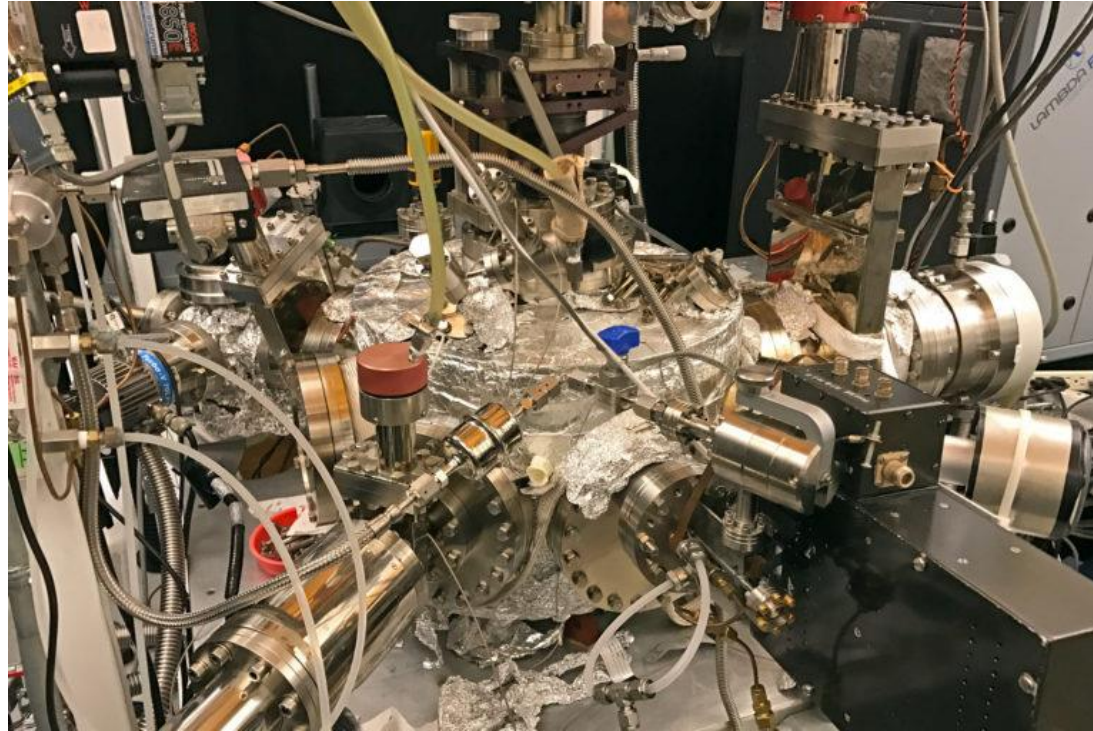

(apparently the making of cyclestar nano tech lube...)

Since FF lube testing there have been a number of new high tech lubes released, and some exciting new ones are on the way. - Some of the new lubes from big respected companies will be claiming some pretty big performance, and I've seen a bit of snippet into some of them that have extremely good friction performance - on a clean chain. But the trick as always is how does a drip lube deal with contamination. Will we find one that stays close to waxing? Or match waxing? Or beat waxing?

A couple of the extreme high end drip lubes – Muc Off Nano and the just released Ceramic Speed UFO drip lube – are extremely fast drip lubes – both have actual proper friction testing equipment so there is actual testing of their performance. The key as always is how do they handle contamination. CS UFO sets to a proper solid so this bodes extremely well, Muc Off I am trying to find out a bit more but appear to be hinging on a very strong protective membrane that delivers extreme high pressure friction performance and be able to protect chain metal for a long time. They claim their lubricant withstands harsher conditions for much longer than any wax based lube or solid wax – so I am excited to see how this tests – as usual actual detail information on testing protocols is not available.

There is another one – Cyclestar Gold – with some rather big claims on tech and performance but with NO data to back up, and if one writes to them (and Im not the only one who has) to ask questions re data and performance – they simply do not answer back. Funnily enough they include a letter with the purchase in case you are interested in being a retailer – so they are happy to talk to you then, but look for some data to back up the big claims and your enquiry is simply consigned to the waste bin. An interesting approach. Here is high tech company boasting about the amazing tech used to create the best lube ever - you would think they would want to talk your ear off about how they ascertained these results to back their claims. I find it odd in the extreme they flat out ignore any correspondence re testing and performance. So that will be interesting to test but for the price and claims their approach to questions is not confidence building. *(Just for fun It is also worth noting all their laser crafted low friction tech is suspended in mineral oil. High grade mineral oil tests at 6w efficiency @ 250w, Cyclestar tests at 7w. So at a quick glance one could be forgiven for thinking a lot of tech has gone into finding a way to make mineral oil slower. And mineral oil is not great on the gathering and dealing with contamination front – so it is hard to see how all the super tech suspended in the mineral oil won't also be negatively affected by contamination. At \$60 for 30ml delivered to my door, I really wish they would answer my questions.*

Careful correlations...

The longevity testing performed here hinges on the correlation between abrasive wear of the pins / plate shoulders and rollers. If a lube was frictionless and remained frictionless, these parts would not wear, and chains would not “stretch” and last forever. There are a number of components of friction in a chain (to properly understand you really need to read full test brief, or at least Friction Facts White Paper – this is just to cover a little for those who haven’t / won’t). There is high pressure friction between pins / plate shoulders / rollers under direct rider load. There is same but low pressure friction as links snake through derailleur pulleys. There is viscous friction as the links articulate, and there is static friction (stiction) as links constantly need to start moving from a static position. And this is happening in around 40,000 friction points per minute. There is so much mechanical work being done by your chain that this is why chains and lubes are where it is at for the biggest and easiest watts savings vs bearings that spin lazily in a sealed environment.

In outright efficiency tests on a clean chain in a lab – the percentage of the overall friction equation that low pressure friction, viscous friction and static friction play will likely be a much greater percentage than on a contaminated chain. On a contaminated chain where the high pressure friction movements are being performed with a lubricant that is now abrasive to some degree – this part of the friction equation will likely grow and grow over “X” km to overshadow the other aspects re overall efficiency being delivered. And it is the high pressure abrasive friction aspect that is responsible for the vast majority of chain wear as it is this that wears the pins and plate shoulders thinner and roller bores bigger.

Hence a lubricant simply cannot be a high efficiency lubricant out in the real world if it is eating through hardened steel parts at a prodigious rate.

Out in the real world different lubricants gather contamination at vastly different rates – are they solid? Contain mineral oil? Carrier fluid with solvent that dries to some degree?

How do they handle the contamination they gather? To what degree do they actually “clean” as they lube, or form protective films / membranes?

So a lubricant that tests well in a lab can start acting like a bastard file in short order once ridden outside. Or one that tests quite mediocre may remain similar to that level for an impressive period slowly changing to something more akin to a mild emery cloth. The mild emery cloth is going to be a lower friction lube with lower chain wear rate than the bastard file and be a better choice of lube unless your race is a short race being held in a laboratory.

However – it is possible that a lubricant can exhibit excellent longevity results but still be a relatively poor efficiency lubricant. It may simply perform poorly in viscous and static friction. An analogy would be heavy duty grease in bearings – it may exhibit excellent bearing life, but fast and high efficiency it will not be vs time trial grease. So the worst efficiency lubes on the FF testing – is it simply that high static and viscous friction contributed heavily to this result and is not necessarily a predictor that it will have a poor longevity result? – that will depend on how well it goes re gathering and dealing with contamination, how abrasive it becomes and its high pressure friction performance. *Maybe it will be like a heavy duty grease and deliver an excellent longevity result – but in this case we know from the efficiency testing this does not translate to a fast lube. It is possible it may be a good choice for your commuter bike etc. Or maybe it will return an average longevity result and so overall just have not a lot going for it.

(we say maybe as stereotypically lubes with poor static and viscous friction are a heavier viscosity wetter lubes, and these tend to gather and hold a lot of contamination quickly. They can be great for riding for hours in the rain and muck and chain still be “lubricated”, but the lubricant can literally become like sandpaper. There is often a big trade off between outright longevity of a lubricant and how contaminated it does or does not become).*

So what we are looking for are the best lubricants that have high outright efficiency and if used and applied correctly as per manufacturer’s instructions deliver impressive wear longevity results and stay very clean. This demonstrates that it does not become notably abrasive and have a big decline in high pressure friction performance - therefore retain great efficiency levels outside the lab.

Where possible we will match longevity results with outright efficiency results if known and freely available. If a lubricant achieves excellent longevity results in our test here however is matched with a fairly medium or poor outright efficiency result – maybe that is good choice of lube for your training bike / commuter but not your race bike / race chain etc.

Where lubes do not have readily available data we will work with manufacturer to see what we can get, and / or try and twist FF arm to test – sometimes they still can't resist ☺

I have asked Friction Fact re testing our chains when they have reached their end of test mark, as that would complete the circle of knowledge – clean chain efficiency, longevity result, end of test contaminated efficiency result. At the moment – the answer is no due to conflict of interest – but I will keep asking, and I will keep all end of test chains in hope of this situation changing in the future.

A bit of a wrap!

- Be wary of “cleans as it lubes” claims – there is huge variability in performance, and a rather loose definition re “clean”.
- Be wary of “forms a protective film / membrane” claims. Again – huge variability in performance.
- Be wary of “conditions the metal” claims
- Current knowledge points to minimising the amount of contamination gathered is generally superior vs ways of trying to handle contamination gathered.
- Solid wax or drip lubes that dry to a proper solid coating have an advantage re contamination, as well as viscous friction (solid lubes have no viscous friction). Dry / Semi dry lubes that go tacky MAY perform well, they also may not.
- Be aware however that a poorly executed dry lube will not give these advantages – one is simply left with very little actual lubricant after carrier fluid has evaporated. They can have very short lifespan, high friction and high parts wear rate.
- Liquid lubes increase in contamination from km zero and the ratio of contamination to lubricant usually continues to build and build, although there are exceptions. Real world friction results will typically be much higher than clean chain lab test results – even the longest lab testing tends to only go to around 4 hours. The friction increases from contamination will correlate with increased rate of

chain wear. If a lubricant gathers very little contamination, and / or truly keeps contamination from acting against chain metal, chain wear rate will be low and friction increases vs its lab performance will low.

- Wax emulsion lubes that go semi dry or “plastic” may have excellent dry contamination resistance, however water will provide a medium for contamination to penetrate, and once in, they can have no effective mechanism of getting back out again. They can also take a lot of time and effort to properly prep after cleaning chain to ensure the viscous lube penetrates through to pin through the very small lubrication gap.
- A chains PTFE coating and any platings can be quickly compromised from abrasive friction leading to an increased rate of friction and chain wear.
- Solid lubricants gather contamination at vastly lower rates, and for a good period after each treatment have two solid lubricating surfaces sliding against each other preventing metal to metal and contamination to metal contact. Hence they can remain close to lab friction performance for an impressive period after each treatment and not begin increasing from km zero. In fact most completely solid wax treatments will show a decrease in friction vs lab tests after the wax has been fully broken in. Consequently they can also deliver extreme chain longevity by truly preventing anything actually coming into contact with chain metal. This is dependent on not exceeding the treatments lifespan for the conditions.
- Note however that solid lubricants – once all of the lubricant has been worn off- friction can increase quickly and dramatically. They need to be kept within the treatments lifespan and so may not be suitable for long wet events or enduro’s unless one is able to re-lube during event.
- To retain good performance most – but not all – drip lubes require frequent full solvent cleans to reset contamination levels in the chain or friction performance will continue to degrade. Some can have a frighteningly quick change in performance vs lab results, some will remain in the ball park of lab results for an impressive period – but without periodic proper cleaning a notable increase in friction and wear is usually inevitable.
- Some drip lubes – usually wax emulsion lubes – can perform better over time without cleaning due to building up of wax layers inside chain and low contamination gathering rate in dry conditions.
- These lubes can have an initial high wear rate due to poor initial penetration to pin through lubrication gap.
- These lubes can also retain high friction and wear rates post wet rides due to lack of vector to shift contamination back out, resulting in need to fully clean chain post wet rides to reset contamination – leading one back to initial issue of getting lube penetrating through to pin again.

- Consider the apparent “convenience” of drip lubes vs “inconvenience” of waxing application. Drip lubes are easier to drip on but require a large amount of cleaning time and care to remain remotely near lab performance, and drive train parts wear will range from poor to good – typically 3000 to 6000km to reach 0.5mm for most road cyclists. Waxing takes a few minutes longer to apply at the front end, however the performance is always very close to lab performance for the lifespan of each treatment, and no cleaning maintenance is required of chain and drivetrain which remain exceptionally clean. Each re wax – being fully immersive in hot wax - resets any small amount of contamination gathered and ensures complete lubrication to all surfaces of the chain. It is the only time re lubing properly cleans as lubes, your chain comes out like brand new every re-wax. Drive train parts longevity can reach simply must experience to believe levels. So for those who never ever clean drivetrain, then yes – waxing will add time. For those who try to stay on top of drip lube drivetrain, waxing usually saves a lot of time due to no cleaning of chain and drivetrain required, and it is always near lab test friction performance as long as kept within its treatment longevity limits.
- A dedicated race chain is a very cheap, smart and simple way of saving a stack of watts for events. This chain can be properly prepped and kept in a very low friction condition and with low wear, as opposed to rocking up to races on same chain that is hammered in training. It costs no more to pre buy next chain, and when training chain hits 0.5 wear, race chain becomes training chain, get new chain to prep for racing chain.

Thanks for reading!

PS - We love questions – so if you have any on any fronts – zing them through to info@zerofrictioncycling.com.au

.....

Summary of tests – full test protocol running sheets available on request.

Best articles to read!!!

http://www.friction-facts.com/media/wysiwyg/Friction_Producing_Mechanisms2.pdf

http://www.velonews.com/2015/12/bikes-and-tech/technical-faq/technical-faq-chain-wear-measurement_390085

http://www.velonews.com/2017/08/bikes-and-tech/ufo-drip-might-be-the-fastest-chain-lube-ever_446861

http://www.velonews.com/2013/04/bikes-and-tech/velolab-revisited-testing-chain-friction-over-time-with-progold_282854

*Note – msw tested at 4.6w on velonews / FF testing. Race chains with break in, ultrasonic cleaning, waxing, break wax in and powdering are something else again. Hence MSW race chains or CS UFO chains will make a lot of sense if you have read everything to this part as well as why we sell wax ☺

<https://cyclingtips.com/2016/05/friction-facts-how-lubricants-and-seals-affect-cartridge-bearing-friction/>

Test equipment : Ultegra 11spd chain on shimano 105 11-28 cassette, Shimano 53/39 chain rings. Industrial 250w motor geared to 100 cadence, coupled to chain set axle. Tacx Neo smart trainer to control load- goal load per interval 250w +/- 2%.

Test protocol outline: (*refer full test brief for full details). Test chain is shimano ultegra 11spd. Chain is initially perfectly cleaned with multiple agitated solvent baths, ultrasonic clean and methylated spirits + acetone rinses. All chains are measured for initial manufacturing tolerance across 7 separate sections of chain accurate to 0.01mm. All check measures

at end of each test block are repeated the same. Simulations are run at as close to 250w +/- 5w resistance window as possible. Each block is 1000km – with both Flat and Hill simulation intervals in every block. Flat simulations are run on large chain ring and alternate through cogs 4, 5, & 6 (21, 19, 17t), hill simulations are run on small chain ring and work through cogs 1, 2 & 3 (28, 25 23t). Intervals on clean blocks are 400km for flat simulation, and 200km for hill simulation. Each interval runs for approximately 10 to 12 hours depending on ratio – and so each 1000km block approx. 30 to 32 hours. Lubrication is applied as per manufacturer instructions, and re-applied either at start of each new intervals as per test protocol (every 400km flat sim, 200km hill sim) – unless according to manufacturer instructions this frequency may be detrimental to performance - in which case re lube intervals will be adjusted and this noted accordingly. During contamination blocks - contamination introduced is sandy loam which is a mix of sand, silt and clay – wet contamination blocks also have water spray. During Dry & Wet contamination blocks, the interval lengths are halved (most cyclists would re lubricate more often if riding in harsher conditions – so every 200km flat and 100km hill simulations. Contamination is introduced mid interval – 100km mark for flat and 50km mark for hill. Extreme contamination block the amount of contamination is doubled, and this is also done twice per interval vs just mid interval. If a lubricant specifies / recommends drying time before riding – this is done – all manufactures instructions are closely followed. Blocks of no contamination are alternated in with blocks of contamination to give lubricants the best chance to prove any “clean as they lube” ability – a common lubricant claim. Contamination is introduced in both dry and wet format – dry the contamination is 5grams of sandy loam released at a controlled rate over the chain whilst running via small nozzle, wet is 500ml of water sprayed at low pressure onto running chain, and 5grams of sandy loam added. During extreme contamination block the amount of contamination (wet and dry) is doubled, and the frequency it is added is doubled. Km's achieved in this test should in no way be interpreted as km's you can expect to achieve in your own riding as the power and contamination you subject your chain and lubricant to will be different, as may be your chain and drive train maintenance – it is expected most should achieve more km's vs this test – the test averages higher watts than most, there are no rolling or descending km's, an overall level on contamination may be higher that what your chain is exposed to. Note this is road simulation and will not be able to be equated to mtb and cx km's as they eat through chains much much faster. The extreme contamination

protocol is more akin to tough off road conditions – however not all lubricants will be test through that protocol if they have not made it that far into the test – if the amount of wear from other blocks has been sufficiently high, it is not going to be a lubricant suited for harsh conditions riding.

**To properly understand testing and results strongly recommend reading Test Protocol Synopsis as a minimum, better yet is to read full test brief and friction facts white paper – you will learn a lot about your most crucial component & its lubrication – it will save you both watts and running cost \$. Full Test protocol running sheet for each lubricant tested is also available on request. All docs freely available from lube test section on www.zerofrictioncycling.com.au*